

Temperature-Dependent Modal Test/Analysis Correlation of X-34 FASTRAC Composite Rocket Nozzle

Andrew M. Brown*

University of North Carolina at Charlotte, Charlotte, North Carolina, 28223

A unique high-temperature modal test and model correlation/update program has been performed on the composite nozzle of the FASTRAC engine for the NASA X34 reusable launch vehicle. The program was required to provide an accurate high-temperature model of the nozzle for incorporation into the engine system structural dynamics model for loads calculation; this model is significantly different from the ambient case due to the large decrease in composite stiffness properties due to heating. The high-temperature modal test was performed during a hot-fire test of the nozzle. Previously, a series of high-fidelity modal tests and finite element model correlation of the nozzle in a free-free configuration had been performed. This model was then attached to a modal-test verified model of the engine hot-fire test stand, and the ambient system mode shapes were identified. A reduced set of accelerometers was then attached to the nozzle, the engine fired full duration, and the frequency peaks corresponding to the ambient nozzle modes individually isolated and tracked as they decreased during the test. To update the finite element model of the nozzle to these frequency curves, the percentage differences of the anisotropic composite moduli due to temperature variation from ambient, which had been used in the initial modeling and which were obtained by small sample coupon testing, were multiplied by an iteratively determined constant factor. These new properties were used to create high-temperature nozzle models corresponding to 10-s engine operation increments and tied into the engine system model for loads determination.

Introduction

THE X-34 air-launched hypersonic rocket plane is a technology demonstrator vehicle being built as part of the NASA reusable launch vehicle program. The goal of the X-34 program is to demonstrate new technologies that can be used to reduce the cost of access to orbit from \$10,000/lb to \$1000/lb. The FASTRAC engine is being designed, analyzed, manufactured, and tested as the main engine for that vehicle. The engine uses a gas-generator turbopump cycle fueled by liquid oxygen-kerosene and is rated to 60,000 lb of thrust. It is designed to be built at a much lower cost than conventional engines, with a small part count, simple assembly procedure, and a rapidly manufactured two-layer composite integral combustion chamber/nozzle (Fig. 1).

Large dynamic loads propagate through the engine due to rocket combustion and from the turbopump. In order to predict the values of these loads for design and analysis, an accurate dynamic finite-element model of the engine is required (MSC/Patran[®] and MSC/Nastran[®] were used for all analyses). The structural backbone of this engine is the nozzle, which all the other components are mounted upon, as seen in Fig. 2. This nozzle is made of a two-layer composite composed of a thermal liner ("composite 1") and a structural overwrap ("composite 2"), presenting new challenges in modeling and testing. The first of these was generating a 360-deg finite-element dynamic model that could be built and correlated in a timely fashion to allow for multiple nozzle and engine test configurations.

This correlation effort was made considerably more difficult because of the anisotropy of the composite materials. This effort has been documented in a previous paper by Brown and Sullivan.¹

A major challenge became clear when it was realized that the dynamic stiffness properties of the nozzle liner would change substantially during the firing of the engine, thereby changing the loads throughout the engine. This change was because of the large temperature dependence of Young's moduli and Poisson's ratios of the composite liner, which had been obtained from coupon testing. Initial predictions of the changes in natural frequencies, presented in Ref. 1, indicated a possible decrease of over 40% by the end of the engine burn. Because this was based on predictions of not only high-temperature material properties, but also on predictions of temperatures, it was clear that a test to verify the actual dynamic properties would be necessary. The determination of the type of test, test description, and correlation to the test are the subjects of this paper.

There has been a limited amount of work previously published on this subject. In 1991, Snyder and Kehoe² performed a detailed experimental and analytical study of aluminum plate specimens that were heated uniformly, nonuniformly, and transiently. The finite element method was used as the analytical baseline for comparison with the experimental results. They found that the natural frequencies decreased, the mode shapes stayed constant, and the damping for some of the modes increased.² That the mode shapes stayed constant was an important result because it implies that the bulk of the effect of the heating was limited to an easily modeled change in the elastic modulus rather than some unknown combination of changes in the modulus and density. In 1993, Kehoe and Deaton followed this study up with similar tests and analysis on titanium and fiberglass plates.³ Some of the important conclusions from this study were that the reduction in material properties due to heating was the primary factor in changes in dynamic characteristics for uniform heating, but that thermal stresses played an equally important role for nonuniform and transient heating. A closed-form analytical solution for a heated anisotropic plate with specified boundary conditions was presented by Locke in 1994 that also compared favorably with finite element analysis.⁴ To the author's knowledge, the study described in the paper is the first published work describing large-scale modal testing and model correlation of complex structures undergoing a significant amount of heating that are composed of materials whose dynamic properties are strongly dependent on temperature.

Presented as Paper 2000-1741 at the AIAA/ASME/ASCE/AHS/ASC SDM 41st Conference, Atlanta, GA, 6 April 2000; received 27 September 2000; revision received 16 October 2001; accepted for publication 17 October 2001. Copyright © 2001 by the American Institute of Aeronautics and Astronautics, Inc. No copyright is asserted in the United States under Title 17, U.S. Code. The U.S. Government has a royalty-free license to exercise all rights under the copyright claimed herein for Governmental purposes. All other rights are reserved by the copyright owner. Copies of this paper may be made for personal or internal use, on condition that the copier pay the \$10.00 per-copy fee to the Copyright Clearance Center, Inc., 222 Rosewood Drive, Danvers, MA 01923; include the code 0748-4658/02 \$10.00 in correspondence with the CCC.

* Visiting Professor, Department of Mechanical Engineering; currently Aerospace Engineer, Structural Dynamics and Loads Group, NASA Marshall Space Flight Center, Marshall Space Flight Center, Alabama 35812. Member AIAA.

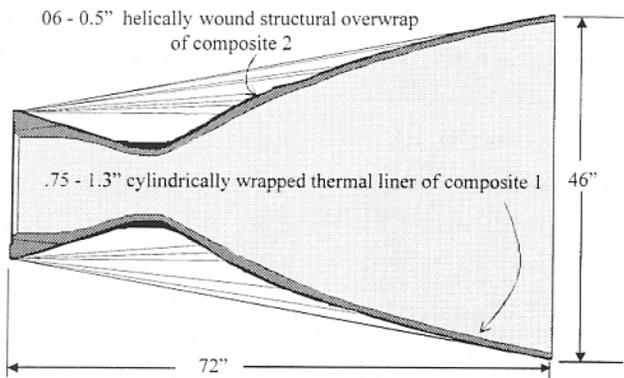


Fig. 1 Cutaway of X-34 FASTRAC rocket nozzle.

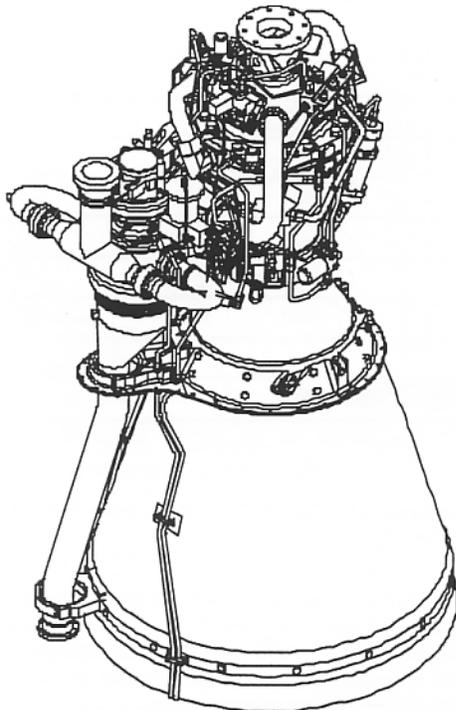


Fig. 2 Turbopump and other FASTRAC components mounted on nozzle.

Approach

A variety of options were discussed for implementation of the test/analysis correlation. The first one considered was to heat the nozzle in large ovens able to cover the expected temperature range. A method for remotely controlling impacts and obtaining acceleration measurements was formulated to perform the modal test in the oven. In the end, however, it was realized that creating an appropriate thermal distribution throughout the nozzle in the oven was impractical. In addition, the temperature of the structural overwrap was not predicted to exceed 200°F during engine burn, and this could not be controlled in the oven. A solution to the problem became apparent when plans were made independently to perform a hot-fire test of the nozzle itself, without any other engine hardware, to satisfy a variety of programmatic goals. This test would be full duration, the temperatures experienced by the nozzle would be the same as expected in an actual mission engine burn, and the nozzle would be isolated from most of the surrounding hardware, which was critical for a reasonable correlation with the detailed nozzle-only model. A decision was, therefore, made to use this hot-fire test to obtain the modal data needed for finite element model correlation.

The plan for the test and correlation consisted of several steps. Initially, a model of the test stand was built to provide accurate boundary conditions for the nozzle, which would be cantilevered off of it. The model was not intended to simulate rigorously every

mode of the stand, but rather just to provide a reasonable model of the interface with the nozzle. A modal test of the stand was performed (see Fig. 3), and the stand model was correlated to some degree, as shown in Table 1.

The next step was to perform an ambient temperature test-stand-nozzle modal test and model correlation. This test was used to identify the modes and natural frequencies of the system that would exist at the beginning of the engine fire. This modal test would verify the model of the test stand combined with a previously free-free modal-test-verified model of the nozzle. This test was performed immediately before the hot fire, but a quick look at the data suggested that the combined structural system introduced families of modes for one of the nozzle's primary modes, first bending, which existed only as a single mode for the nozzle in its free-free configuration (see Fig. 4). This family consisted of different modes where sections of the test stand, such as the front mounting plate, would move in or out of

Table 1 Test stand only test/analysis comparison

Mode	Description	Analysis, Hz	Test, Hz
1	Main Structure, front plate side to side	24.0	23.8
2	Predominantly plate up and down	48.4	50.0
3	Plate diagonal twisting about vertical axis	61.54	68.51

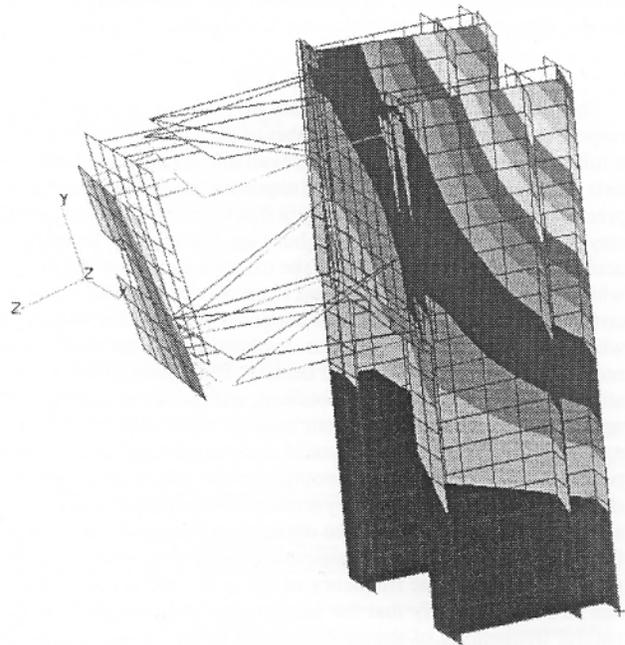


Fig. 3 Test stand, mode 2 at 50 Hz (deformed shape superimposed on undeformed shape).

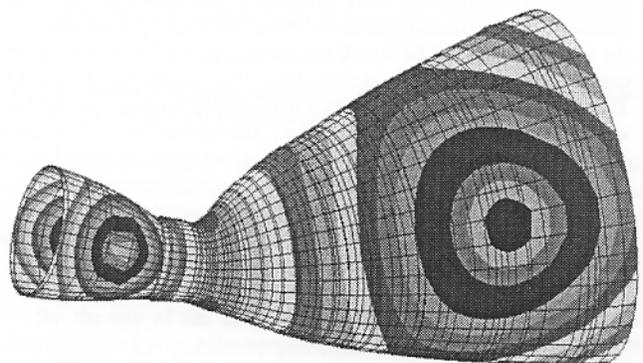


Fig. 4 Nozzle, free-free, first bending at 180.9 Hz.

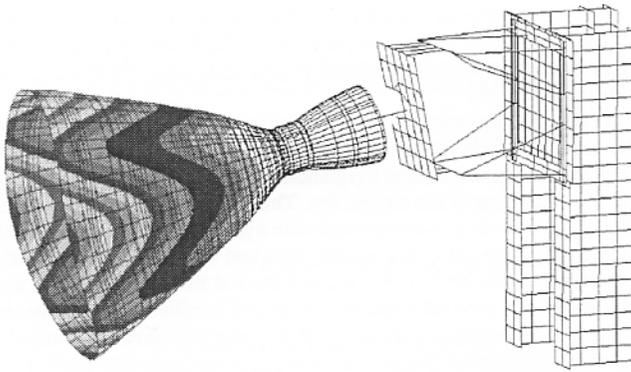


Fig. 5 Two ND mode of nozzle on test stand.

phase with the nozzle first bending. These modes were so numerous that it would be very difficult to update a finite element model to match them. Fortunately, the nozzle nodal-diameter modes remained somewhat isolated from the interface with the boundary condition (Fig. 5). This allowed the hot-fire modal-test plan to proceed, where only the nodal-diameter modes of the nozzle-test-stand model would be used for correlation. These modes are not sufficient by themselves for correlating a model because the nodal-diameter modes do not fully account for the effect of longitudinal Young's modulus E_L (which is independent of Young's moduli in the other directions), so that this process forced an assumption that the temperature effects on the other material constants were also applicable to E_L .

Hot-Fire Test

The plan for the hot-fire modal test would be to measure only the response, using a subset of the number of accelerometers needed for a full-scale modal test because the available instrumentation channels were limited due to the other requirements of the test. Special precautions had to be taken to ensure that the accelerometers would stay on the nozzle and would not burn up. Fortunately, because the accelerometers were installed on the external surface of the nozzle, which was not expected to exceed a temperature of 200°F, merely covering them with fire tape was adequate. Because the excitation, which would be generated by the combustion process itself, could not be measured, power spectral density (PSD) plots of the acceleration response only would be obtained, with peaks occurring at the natural frequencies of the system because there were no pure harmonic forcing functions that would show up independently. These peaks would be tied to their appropriate mode shapes at the initiation of the test using the preliminary ambient temperature modal test results described. PSDs would be obtained at frequent time intervals throughout the test, and by combining these plots into a waterfall plot, the change in the frequency of the peaks with respect to time can be seen. To verify that the frequencies being tracked were the natural frequencies of the specific mode shapes being sought, the PSDs of the different accelerometer locations would be compared to obtain rough mode shapes.

The hot-fire test was performed in late November 1998. Several measures of data quality were performed, and only 2 of the 12 accelerometers apparently debonded from the nozzle. Examination of the waterfall plots of the remaining instruments showed that the frequency peaks were clearly defined and could be tracked as planned. The time history of each frequency peak was then extracted from the waterfall plots for model correlation. The history for one of these accelerometers tracking the fundamental two nodal-diameter mode of the nozzle is shown in Fig. 6. In addition, comparison of the relative magnitudes for different accelerometers verified that the mode shapes associated with the peaks were the ones obtained from the ambient modal test and that the proper mode was being tracked.

Thermal Model

An essential step in the modeling procedure was applying the correct temperature to the different locations in the nozzle as it heats up during the test. This information was obtained by using

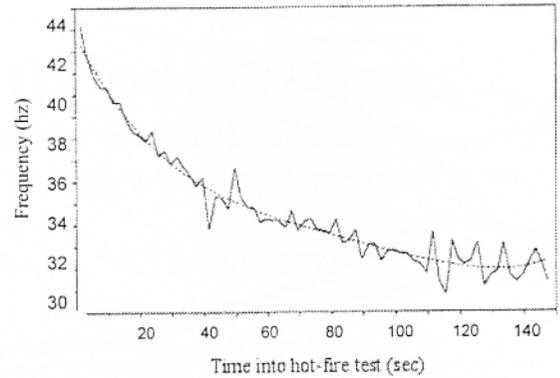


Fig. 6 Isolated time history trace of two ND mode frequency peak for accelerometer 11.

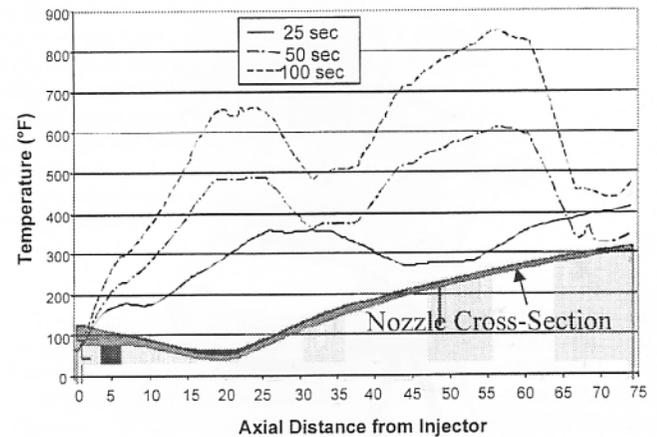


Fig. 7 Temperature of nozzle for various times into hot-fire test vs axial location.

temperature probes during the test to correlate a thermal model of the nozzle, which had been built previously and was used for the initial estimates of the natural frequency decline. After this thermal correlation was completed, a complete profile of the average bulk temperature of the inner composite layer for each axial position of the nozzle at 0, 25, 50, 100, and 150 s into the test was generated. (Because there was very little difference between the values at 100 and 150 s, the 100–150 s increment was ignored at this point.) A plot of these temperatures vs the axial location along the nozzle is shown in Fig. 7. (A cross section of the nozzle is also superimposed for illustrative purposes.) The bulk value was chosen because two-dimensional composite plate elements were used in the finite element model, and so temperature variation in the transverse direction would not be able to be used. By the use of a linear interpolation between these time profiles, the temperature at any location at any time into the test was generated.

Model Correlation

Any of a number of methods could now be applied to obtain the desired test-verified hot model of the nozzle. Previous work discussed earlier indicates that both the variation in stiffness properties and the thermal stress play a role in the change in natural frequencies for the transient heating conditions that existed in the hot-fire test, but for simplification and timeliness it was originally assumed that the material properties were solely responsible for the change. This assumption has been verified after the completion of the engine program by performing a complete nonlinear modal analysis, which incorporates the effect of the thermal stresses due to the differential heating of the nozzle. Coefficients of thermal expansion as a function of temperature obtained from coupon testing were first transformed to the finite element coordinate system as explained in Ref. 1. The transformed properties were then input into the model

Table 2 Original and altered composite material constants as a function of temperature

Temperature, °F	E warp/ 1000, psi	E fill/ 1000, psi	E norm/ 1000, psi	ν Warp fill	ν Norm warp	ν Norm fill	G warp fill/ 1000, psi	G warp norm/ 1000, psi	G fill norm/ 1000, psi
<i>Original properties</i>									
70	2810	2810	2000	0.18	0.21	0.21	894	535	535
250	2690	2690	1400	0.14	0.19	0.19	850	438	438
350	2440	2440	1080	0.12	0.19	0.19	596	401	401
400	2360	2360	780	0.1	0.18	0.18	484	322	322
450	2280	2280	540	0.08	0.17	0.17	413	253	253
500	2190	2190	292	0.07	0.16	0.16	340	177	177
550	2090	2090	224	0.07	0.15	0.15	324	166	166
600	2010	2010	177	0.06	0.14	0.14	316	153	153
750	1800	1800	102	0.05	0.11	0.11	273	146	146
900	1660	1660	59.9	0.04	0.1	0.1	256	151	151
1050	1510	1510	51.5	0.04	0.1	0.1	245	159	159
1200	1350	1350	50.8	0.04	0.1	0.1	245	179	179
1500	1090	1090	51.6	0.04	0.12	0.12	207	199	199
<i>Altered properties factor on slope</i>									
70	1.2	1.2	1.02	1.2	1.2	1.2	1.2	1.2	1.2
250	2666	2666	1388	0.132	0.186	0.186	841.2	418.6	418.6
350	2366	2366	1062	0.108	0.186	0.186	536.4	374.2	374.2
400	2270	2270	755.6	0.084	0.174	0.174	402	279.4	279.4
450	2174	2174	510.8	0.06	0.162	0.162	316.8	196.6	196.6
500	2066	2066	257.8	0.048	0.15	0.15	229.2	105.4	105.4
550	1946	1946	188.5	0.048	0.138	0.138	210	92.2	92.2
600	1850	1850	140.5	0.036	0.126	0.126	200.4	76.6	76.6
750	1598	1598	64.04	0.024	0.09	0.09	148.8	68.2	68.2
900	1430	1430	21.1	0.012	0.078	0.078	128.4	74.2	74.2
1050	1250	1250	12.53	0.012	0.078	0.078	115.2	83.8	83.8
1200	1058	1058	11.82	0.012	0.078	0.078	115.2	107.8	107.8

Table 3 Final comparison of test and analytical natural frequencies

Mode	Test at 0 s			Test at 25 s			Test at 50 s			Test at 100 s		
	Analytical at 0 s	% error	Analytical at 25 s	% error	Analytical at 50 s	% error	Analytical at 100 s	% error				
2ND	45.5	46.7	-3	37.3	40.3	-8	35	37.7	-8	32.7	33.3	-2
3 ND	113.4	118.3	-4	94.5	99.2	-5	88.5	95.4	-8	81.4	83.2	-2
4 ND	210.4	221	-5	177.2	183.7	-4	165.5	176.6	-7	154	154	0
5 ND	334.4	357	-7	284	293.3	-3	265	280.2	-6	244	243.8	0
Balloon 2ND	385	357	7	357.5	325.7	9	344	291.6	15	330	264.1	20

according to the nozzle temperature distribution at 100 s, which had been obtained from the hot-fire test. The nonlinear modal analysis was then performed, and the results were almost identical to those when the thermal stress effect was ignored, with a 2.9% increase for the fundamental nozzle mode and decreasing errors for higher-frequency modes.

The correlation was, therefore, obtained solely by perturbing the original material modulus properties vs temperature chart until a reasonable level of model/test agreement was achieved. Of course, the definition of reasonable agreement with test is subject to considerable variation. In this case, the frequencies for several of the higher modes were not in agreement even at the beginning of the test, and so it would not make sense to try to match exactly the frequencies at the end. It was decided instead to try to match the rate of decline in natural frequency to obtain the true effect of the temperature. The most straightforward method to achieve this goal was to multiply the percent decrease at a particular temperature of all of the properties from their baseline value at 70°F by some constant. After several iterations, a factor of 1.2 was determined for all of the properties but Poisson's ratio ν , which required a factor of 1.05. The results of applying this factor on the material properties is shown in Table 2.

Table 3 shows the final natural frequency test/analysis comparisons after model correlation, and Fig. 8 shows the decline of each of the modes (analytically and experimentally) vs time into the test. The modal descriptions in the chart legend are 2ND for the two nodal-diameter (ND) mode, 3ND for the three ND mode, etc., Balloon 2ND refers to a mode that has a two ND shape just aft of the throat

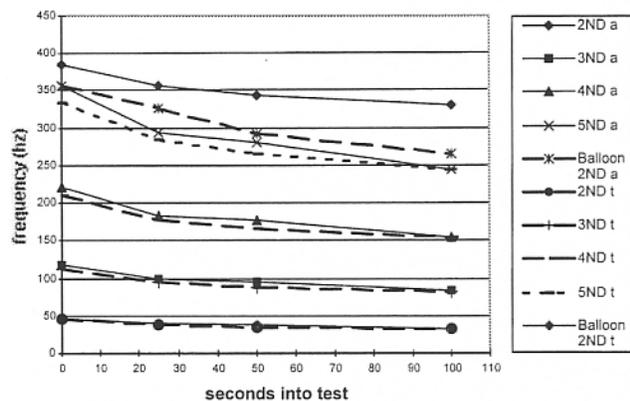


Fig. 8 Comparison of variation in natural frequencies vs time into hot fire between test and correlated analytical results.

in addition to another two ND shape out of phase with it near the exit plane. Final correlation consisted of qualitatively matching the test/analysis frequency curves as well as using the quantitative error measures.

Model Implementation

By the use of the newly correlated material property vs temperature profile and the new nozzle location temperature profiles, complete nozzle models representing the material properties at 10-s increments into hot-fire were then generated. These models were

supplied to the total engine system model for loads generation at these increments, which is discussed in a paper by Frady.⁵

Sources of Error

There are several sources of error in this correlation procedure. Discrepancies probably exist due to some modeling errors as discussed in Ref. 1, the lack of good longitudinal test modes to correlate E_L to, and the scaling method used to alter the material properties table. In addition, the transverse variation in temperature was not accounted for; evaluation of the magnitude of this error could be estimated by comparison with a solid finite element model of the composite, which has not been performed here. However, the final results indicate that no large inconsistencies exist within the model itself (which can occur by locally varying stiffnesses to match test data, for instance), and that a usable high-temperature model was created that matches the modal properties during hot fire. Because the original model (at ambient temperature conditions) had been test verified with an extensive series of tests, and the thermal distribution was also derived from a test-verified model, the error in the small-sample coupon measurements from the as-built case seemed to be the most likely source of discrepancy. The assumptions used also allowed the creation of this model in a timely fashion, which was important because it was critically needed for engine system loads analysis.

Conclusions

A unique high-temperature modal test and finite element model correlation/update program was performed on the X-34 FASTRAC composite rocket nozzle for loads prediction during engine operation. The modal test was actually performed as part of a standard full-duration hot-fire test of the nozzle by itself, which simulated the

actual operation of the FASTRAC engine. A detailed preliminary series of modal tests of the structural components of the nozzle/test stand system was first performed at ambient conditions to baseline the modes and natural frequencies. Waterfall PSD plots using a reduced set of accelerometers were then used to track the modes during the hot-fire test. The finite element model was updated to match the decline in natural frequencies by scaling the decrease of the predicted material property for each temperature. The temperature distribution of the model was obtained by using a thermal model of the nozzle that was also correlated from the same hot-fire test. The new material property curves were used to create a series of high-temperature models representing the structural dynamic characteristics of the engine at 10-s increments into operation. These models were then tied into the structural dynamic model of the entire engine for interface dynamic loads calculation. This approach can potentially be generalized as a method for correcting modulus vs temperature coupon testing to actual composite layups.

References

- ¹Brown, A. M., and Sullivan, R., "Dynamic Modeling and Correlation of the X-34 Composite Rocket Nozzle," NASA TP-1998-208531, July 1998.
- ²Snyder, H. T., and Kehoe, M. W., "Determination of the Effects of Heating on Modal Characteristics of an Aluminum Plate with Application to Hypersonic Vehicles," NASA TM 4274, 1991.
- ³Kehoe, M. W., and Deaton, V. C., "Correlation of Analytical and Experimental Hot Structure Vibration Results," NASA TM 104269, 1993.
- ⁴Locke, J. E., "Vibration Analysis of Heated Anisotropic Plates with Free Edge Conditions," *Journal of Aircraft*, Vol. 31, No. 3, 1994, pp. 696-702.
- ⁵Frady, G., "Engine Systems Loads Development for the Fastrac 60-K Flight Engine," AIAA Paper 2000-1612, April 2000.